Effects of Sulphuric Acid in Mixing and Curing Water on Strength of High-Performance Phosphogypsum Concrete

E. Arunakanthi
Department of Civil Engineering
JNTUACEA, Ananthapuramu, Andhra Pradesh, India

H. Sudarsana Rao
Department of Civil Engineering
JNTUACEA, Ananthapuramu, Andhra Pradesh, India

Abstract

This paper presents the results of an experimental investigation carried out to study the effect of aggressive chemical environment on High performance concrete with phosphogypsum in which Ordinary Portland cement is partially replaced by 20% of phosphogypsum by weight and aggressive chemical environment is simulated by subjecting the concrete to different concentrations of Sulphuric acid (H2SO4) in deionised water during mixing and curing. Compressive strengths and split tensile strengths were determined at 7, 28 and 90 days. The results indicate that the compressive strength and split tensile strength decrease with the increase in concentration of Sulphuric acid when compared with concrete without Sulphuric acid in mixing and curing water.

Keywords: Ordinary Portland cement, High-Performance concrete, Phosphogypsum, Compressive strength, Split tensile strength, Sulphuric acid

I. INTRODUCTION

Any concrete which satisfies certain criteria proposed to overcome limitations of conventional concretes may be called High-Performance-Concrete (HPC). It may include concrete which provides either substantially improved resistance to environmental influences (durability in service) or substantially increased structural capacity while maintaining adequate durability. Nima Farzadni et al. (2011) say that with a fast population growth and a higher demand for housing and infrastructure, accompanied by recent developments in civil engineering, such as high-rise buildings and long-span bridges, higher compressive strength concrete is needed [10]. Currently, high-performance concrete is used in massive volumes due to its technical and economic advantages. Such materials are characterized by improved mechanical and durability properties resulting from the use of chemical and mineral admixtures as well as specialized production processes.

Phosphogypsum is a byproduct of the processing of phosphate ore; mainly in the production of fertilizers. In the field of construction activities, Florida Institute for Phosphate Research (FIPR) elected to investigate the use of phosphogypsum in wallboard and other related products. Marcelo and Alexandre (1982) investigated the properties of cement-stabilized phosphogypsum mixes as potential materials for base and sub-base construction, as well as seeking a non-pollutant alternative to discard large quantities of the material [7]. In order to investigate the possibility of using phosphogypsum in construction, a comprehensive experimental program has been carried out by Mohammad Akour (1993) [9].

Bellmann and J. Stark studied the role of calcium hydroxide in the formation of thaumasite [3]. P.K.Mehta et.al. studied sulphate attack on concrete can lead to expansion, strength loss and ultimately to disintegration [8]. This behavior is due to a reaction of hardened cement paste with sulphate ions from the environment to ettringite, gypsum and thaumasite [4]. Kohler et. al,studied the effect of ettringite on thaumasite formation [6].

Arunakanthi et.al., studied the effect of Hydrochloric acid in mixing and curing water on strength of High-Performance Metakaolin concrete [1] and the effect of Sulphuric acid in mixing and curing water on strength of High-Performance Metakaolin concrete [2]. The present investigation presents the effect of H_2SO_4 on strength properties of HPC with and without phosphogypsum for various concentrations of H_2SO_4.

II. EXPERIMENTAL PROGRAM

A. Materials:

1) Cement:

Ordinary Portland (53 grade) cement of Ultratech brand was used. It was tested as per Indian Standards Specifications IS: 8112-1989. Its properties are specificgravity 3.1, normalconsistency of 33%, fineness of 5%, initial setting time is 105 minutes and final setting time is 350 minutes.

All rights reserved by *www.ijste.org*

2) Fine Aggregate:
The locally available natural river sand was used as fine aggregate. It was tested as per Indian Standard Specification IS: 383-1970. Its fineness modulous is 2.69 and specific gravity is 2.7.
3) Phosphogypsum:
The Phosphogypsum used in the investigation was obtained from Coromandel international Ltd, Ennore, Chennai. The Phosphogypsum passing through 90μ sieve was used throughout the experiment. The specific gravity of Phosphogypsum was found to be 2.34.
4) Super-Plasticizer:
GLENIUM B233 is the super-plasticizer of BASF Company. The properties are Aspect: Light brown liquid, Relative Density: 1.08 ± 0.01 at 25°C, PH: >6, Chloride ion content: < 0.2%

B. Variables Studied:

1) Concrete mix: The mix ratio of cement: sand: corse aggregate is 1:0.76:1.8 with water/ binder ratio as 0.3. The dosage of superplasticizer is 1% by weight of cement. 20 % of Cement was replaced with of Phosphogypsum.
2) Mixing and curing environment: Four different concentrations of H_2SO_4 (50 mg/L, 100 mg/L, 400 mg/L and 800 mg/L) were adopted during the mixing in the deionised water and cured in same condition.
3) Exposure period: Specimens were tested periodically after the specified curing periods of 7, 28 and 90 days.
4) Size of specimens: 150mm x150mm x 150mm size of cubes for compressive strength test and 150mm dia- 300mm height of cylinders for split tensile strength test.
5) Samples for XRD and SEM testing: The cubes with maximum concentration of H_2SO_4 after 90 days testing are collected and grinded and sieved under 40 micron sieve. This powder sample is sent for XRD testing and the broken pieces of cube samples are sent for SEM testing. A total of 135 cubes and 135 cylinders were cast in the laboratory. After 72 hours, all the specimens were demoulded and cured in water in a curing tank at room temperature. After specific exposure period, specimens were tested for compressive strength, split tensile strength in accordance with test procedure IS 516: 1959 [5].

III. RESULTS AND DISCUSSION

A. Effect of H_2SO_4 on Compressive Strength:

The effect of H_2SO_4 concentration on the compressive strength and split tensile strength of HPC with and without phosphogypsum is presented in tables: 1, 2, 3 and 4 and figures 1, 2, 3 and 4. Continuous decrease in compressive strength and splittensile strength is observed with the increase in concentration of H_2SO_4 for both HPCs. If the difference is less than 10% the change is considered to be negligible and if the difference is more than 10% the change is considered to be significant. It is observed that there is significant decrease in both compressive strength and split tensile strength of both HPC's from 100 mg/L concentration of H_2SO_4. The percentage change in compressive strength and splittensile strength of HPC with and without phosphogypsum increased with the increase in concentration of H_2SO_4. The XRD and SEM results show the formation of Calcium silicate hydrate (C-S-H gel) and Portlandite ($Ca(OH)_2$) in both samples without H_2SO_4. But the intensities of C-S-H gel and Portlandite differ in two samples. The XRD patterns corresponding to HPC without phosphogypsum and HPC with phosphogypsum are shown in figures 3 and 5. By analyzing the XRD patterns of samples of two HPC's, the formation of C-S-H gel and Portlandite are formed at angles as shown in table 5 and 6. The intensity of C-S-H gel is more and the intensity of Portlandite is less for HPC with phosphogypsum when compared with HPC without phosphogypsum. This may be the cause for the strengths of HPC with phosphogypsum to be high under aggressive environment. The XRD tests are conducted for the two samples after 90 days with 800 mg/L concentration (maximum) of H_2SO_4. It is observed that inaddition to the compounds formed above, a compound named Thaumasite **(**$Ca_3Si(SO_4)_2(OH)_{6.9H2O}$**)** is formed in both HPC's with H_2SO_4. So the decrease in strengths may be due to the formation of Thaumasite. The angles at which the compounds are formed is shown in the table 4. The XRD patterns are shown in figures 5 and 6 respectively. The compound Thaumasite is hexagonal and dipyramidal in structure. This is fibrous and looks like crystals made up of fibers. This has very brittle fracture producing small conchoidal fragments. This is of massive and fibrous form.

The probable chemical reaction upon the hydration of cement with mixing water containing H_2SO_4 concentration is

$$2H_2SO_4 + SiO_2 + 3CaO + 10H_2O \longrightarrow Ca_3Si(SO_4)_2(OH)_6.9H_2O$$

In tables and graphs CHPC is HPC without phosphogypsum and PHPC is HPC with phosphogypsum

Table - 1
Compressive strength in N/mm^2 for different concentrations of H_2SO_4

S No	*Dosage of H_2SO_4 mg/L*	*Compressive strength (N/mm^2)*					
		7 days		*28days*		*90 days*	
		CHPC	*PHPC*	*CHPC*	*PHPC*	*CHPC*	*PHPC*
1	*0*	*39. 5*	*44.0*	*58.0*	*65.0*	*63. 5*	*68.0*
2	*50*	*36. 8*	*41.7*	*52. 9*	*60.2*	*57.7*	*62.1*
3	*100*	*29. 6*	*33. 8*	*39.8*	*46.6*	*39.1*	*46.0*
4	*400*	*24.9*	*31.0*	*34.7*	*42.5*	*34.0*	*41.9*

All rights reserved by *www.ijste.org*

5	*800*	*21.6*	*28.7*	*29.6*	*39.8*	*28.8*	*39.1*

Table - 2

%age change in compressive strength for different concentrations of H_2SO_4

S No	*Dosage of H_2SO_4 mg/L*	*Percentage change in Compressive strength*					
		7 days		*28days*		*90 days*	
		CHPC	*PHPC*	*CHPC*	*PHPC*	*CHPC*	*PHPC*
1	*0*	*0.00*	*0.00*	*0.00*	*0.00*	*0.00*	*0.00*
2	*50*	*-6.05*	*-5.32*	*-8.81*	*-7.45*	*-9.01*	*-8.64*
3	*100*	*-24.50*	*-23.23*	*-31.26*	*-28.24*	*-38.34*	*-32.34*
4	*400*	*-36.45*	*-29.53*	*-40.24*	*-34.61*	*-46.34*	*-38.24*
5	*800*	*-44.89*	*-34.63*	*-48.93*	*-38.66*	*-54.61*	*-42.45*

Table - 3

Split tensile strength in N/mm^2 for different concentrations of H_2SO_4

S No	*Dosage of H_2SO_4 mg/L*	*Split tensile strength (N/mm^2)*					
		7 days		*28days*		*90 days*	
		CHPC	*PHPC*	*CHPC*	*PHPC*	*CHPC*	*PHPC*
1	*0*	*4.19*	*4.64*	*5.35*	*5.64*	*4.19*	*5.67*
2	*50*	*3.93*	*4.38*	*4.86*	*5.22*	*3.93*	*5.15*
3	*100*	*3.15*	*3.54*	*3.68*	*4.04*	*3.15*	*3.49*
4	*400*	*2.64*	*3.26*	*3.18*	*3.68*	*2.64*	*3.03*
5	*800*	*2.31*	*3.02*	*2.73*	*3.45*	*2.31*	*2.57*

Table - 4

%age change in split tensile strength for different concentrations of H_2SO_4

SNo	*Dosage of H_2SO_4 mg/L*	*Percentage change in Split tensile strength*					
		7 days		*28days*		*90 days*	
		CHPC	*PHPC*	*CHPC*	*PHPC*	*CHPC*	*PHPC*
1	*0*	*0.00*	*0.00*	*0.00*	*0.00*	*0.00*	*0.00*
2	*50*	*-6.24*	*-5.56*	*-9.02*	*-7.48*	*-9.05*	*-8.82*
3	*100*	*-24.81*	*-23.68*	*-31.27*	*-28.35*	*-38.42*	*-32.38*
4	*400*	*-36.82*	*-29.75*	*-40.42*	*-34.72*	*-46.43*	*-38.36*
5	*800*	*-44.95*	*-34.92*	*-48.94*	*-38.68*	*-54.63*	*-42.52*

Table - 5

Compounds and their intensities for samples of HPC's without H_2SO_4

SNO	*Angle in degrees*	*Compound*	*Intensity*	
			CHPC	*PHPC*
1	*12.58*	*C-S-H Gel*	*76*	*128*
2	*17.94*	*Portlandite*	*266*	*122*
3	*21.18*	*C-S-H Gel*	*32*	*62*
4	*24*	*Portlandite*	*110*	*82*
5	*34.34*	*C-S-H Gel*	*124*	*152*
6	*37.3*	*C-S-H Gel*	*34*	*54*
7	*42.24*	*Portlandite*	*64*	*46*
8	*50.76*	*C-S-H gel*	*90*	*106*

Table - 6

Compounds and their intensities for samples of HPC's with H_2SO_4

SNO	*Angle in degrees*	*Compound*	*Intensity*	
			CHPC	*PHPC*
1	*10.34*	*C-S-H gel*	*60*	*68*
2	*11.04*	*Thaumasite*	*74*	*56*
3	*16.16*	*C-S-H gel*	*36*	*50*
4	*21.08*	*Thaumasite*	*160*	*90*
5	*31.6*	*C-S-H gel*	*66*	*84*
6	*35.3*	*Portlandite*	*94*	*78*
7	*41.42*	*C-S-H gel*	*54*	*48*
8	*42.74*	*C-S-H gel*	*42*	*52*
9	*46.02*	*Thaumasite*	*68*	*62*
10	*50.38*	*Thaumasite*	*114*	*106*
11	*53.36*	*Portlandite*	*60*	*44*
12	*53.46*	*Portlandite*	*62*	*42*

All rights reserved by *www.ijste.org*

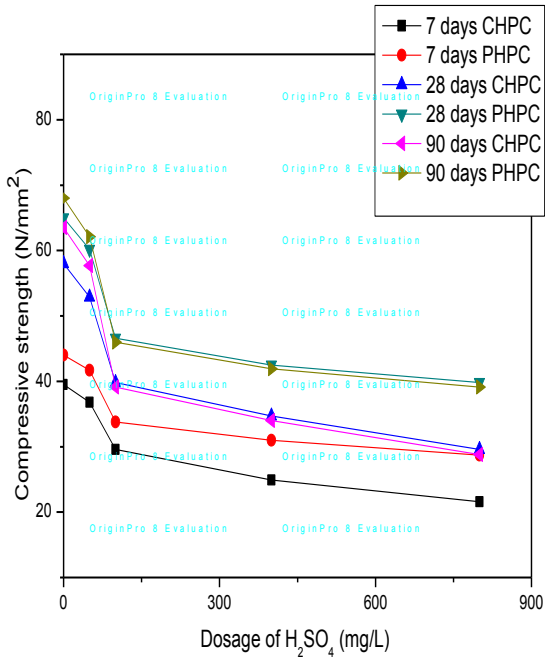

Fig. 1: compressive strengths

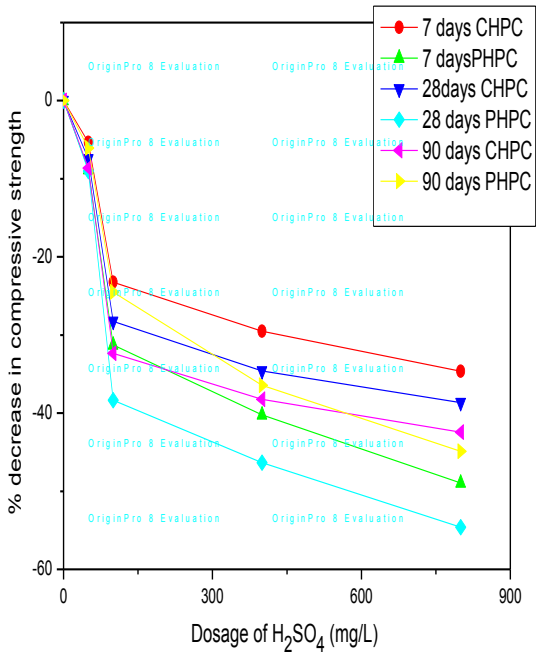

Fig. 2: percentage decrease of compressive strengths

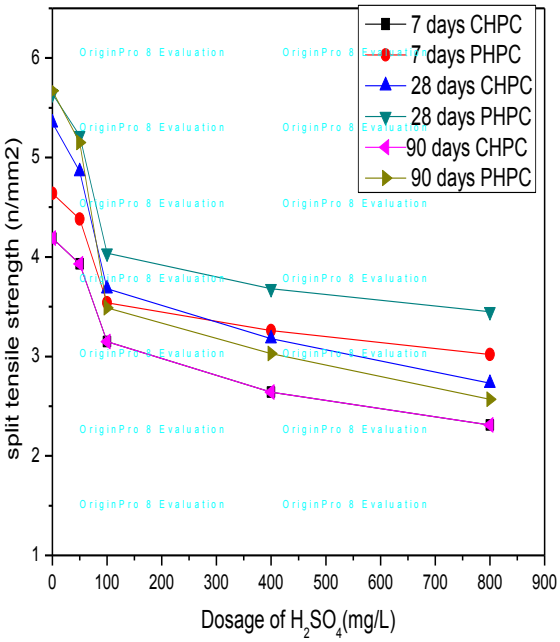

Fig. 3: splittensile strengths

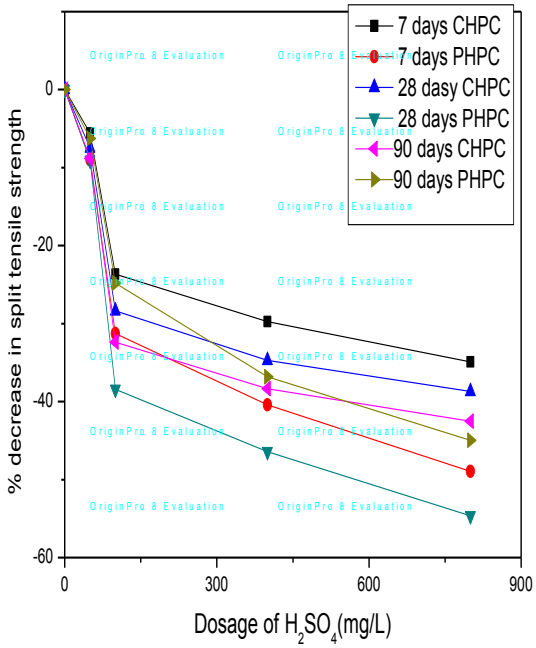

Fig. 4: percentage decrease of splittensile strengths

All rights reserved by *www.ijste.org*

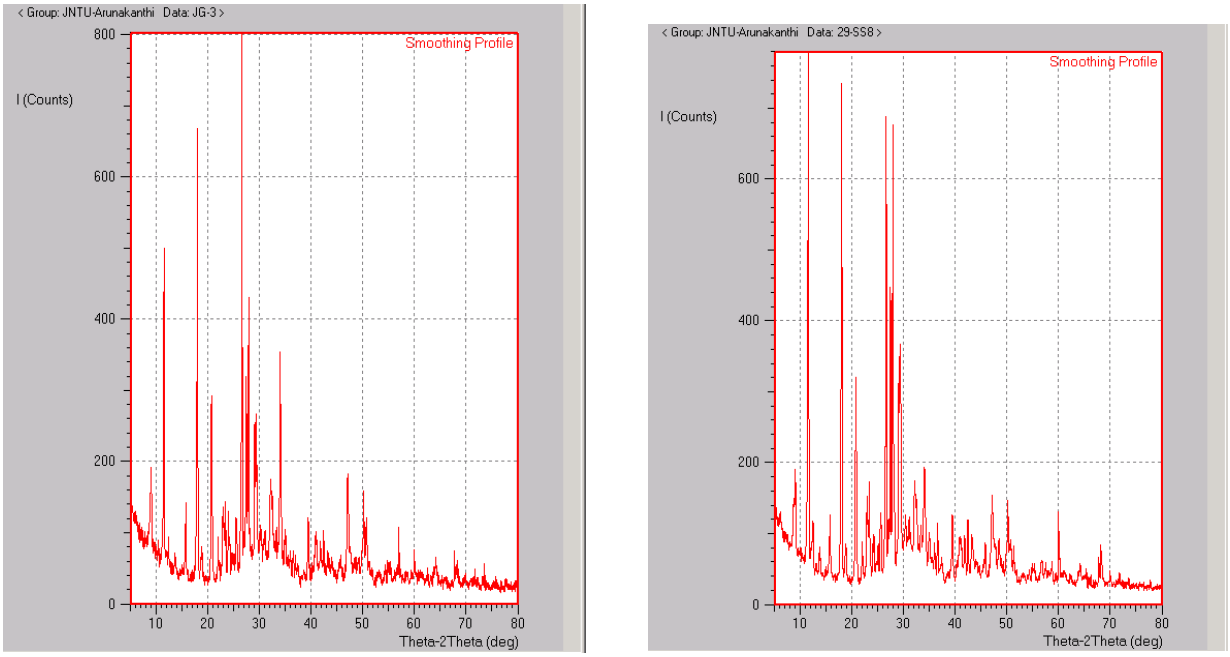

Fig. 5: XRD pattern of HPC i) without Phosphogypsum ii) with Phosphogypsum

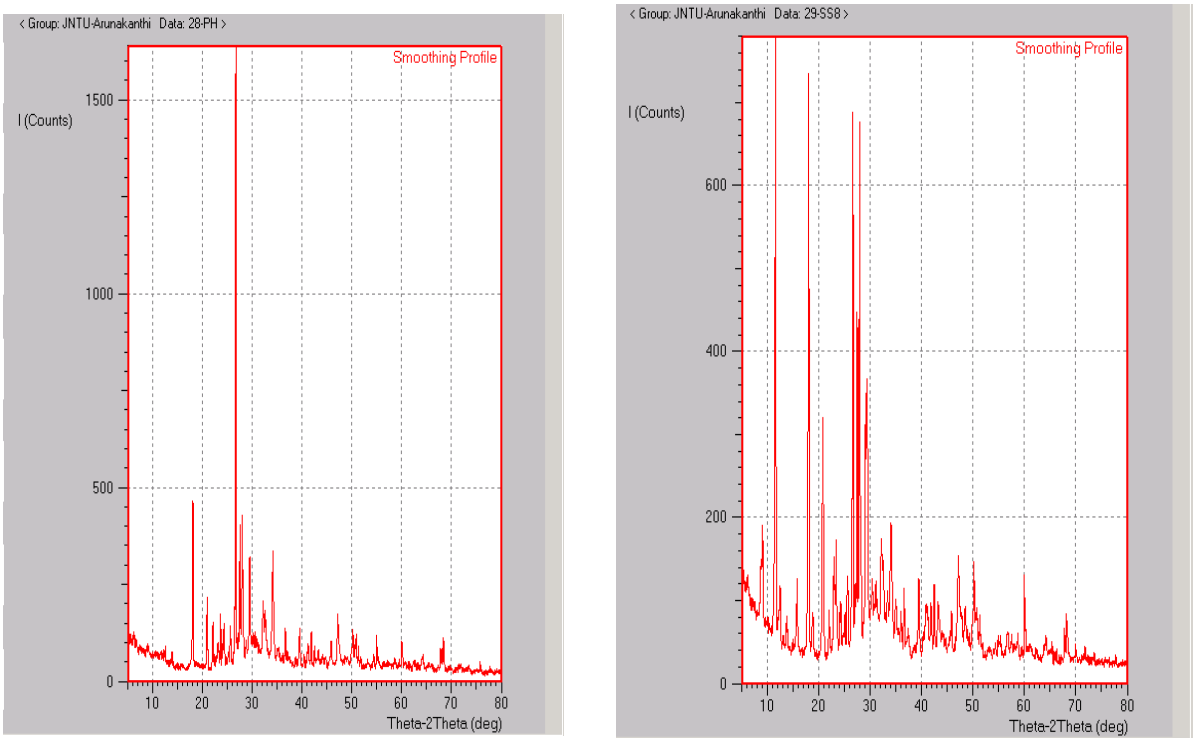

Fig. 6: XRD pattern of HPC i) without Phosphogypsum + H_2SO_4 ii) with Phosphogypsum + H_2SO_4

IV. CONCLUSIONS

Based on the above results of the investigation conducted on High-performance concrete with partial replacement of cement by 20% phosphogypsum and subjected to various concentrations of H_2SO_4, the following conclusions can be drawn:

1) Compressive strength and split tensile strength of HPC increased with the replacement of cement by 20% phosphogypsum. And the strengths decreased with the increase in concentration of H_2SO_4 in mixing and curing water.
2) Compressive strength and split tensile strength increase as the curing period decreases for later ages of curing i.e., 7 days, 28 days and 90 days for 20% phosphogypsum and for all concentrations of H_2SO_4.
3) From XRD studies it is concluded that the formation of C-S-H gel with more intensity and Portlandite with less intensity may be responsible for more strengths of HPC with phosphogypsum.

All rights reserved by *www.ijste.org*

4) From XRD studies it is concluded that the formation of compound Thaumasite may be responsible for decrease in strengths with the increase in concentration of H_2SO_4.

REFERENCES

[1] Arunakanthi. E., Sudarsanarao,H., and Ramanareddy,I.V, (2012), Effects of hydrochloric acid in mixing and curing water on strength of high-performance metakaolin concrete. International journal of applied engineering and technology, Vol.2, No.2 pp.68-76.
[2] Arunakanthi, E., Sudarsanarao,H., (2013), Effects of Sulphuric acid in mixing and curing water on strength of high-performance metakaolin concrete. International journal of Scientific Research, Vol.2, No.12, pp.147-150.
[3] Bellmann.F. Stark.J., (2008), the role of calcium hydroxide in the formation of thaumasite. Cement and concrete Research journal, Vol.38, pp.1154-1161.
[4] Department of Environment, transport and regions, the thaumasite form of sulfate attack: Risks, diagnosis, remedial works and guidance on new construction, Report of the thaumasite expert group, DETR, London [1999].
[5] IS 516: 1959, Standard Method of test for strength of concrete?
[6] Kohler S., Heinz .D. Urbonas L. (2006). Effect of ettringite on thaumasite formation. Cement and concrete research journal, V0l.36. pp.697-706.
[7] Marcelo and Alexandre. (1982). Properties of cement stabilized phosphogypsum.
[8] Mehta.P.K. Monteiro P.J.M. [1993], Concrete-Microstructure properties and materials, Mc Graw-Hill, Newyork.
[9] Mohammad Akour, (1993). Phosphogypsum. Cement and Concrete Research Volume 29, Issue 9, pp. 1419-1425.
[10] Volume 29, Issue 9, pp. 1419-1425.Nima Farzadnia, Abang Abdullah Abang Ali and Ramazan Demirboga, (2011). Incorporation of mineral admixtures in sustainable High-performance concrete. International Journal of sustainable construction Engineering and technology, Vol 2, (1).

All rights reserved by *www.ijste.org*